

# State of the Art: Process of Pozzolan Formation from Ash and its Applications

## Estado del arte: proceso de formación de puzolanas a partir de cenizas y sus aplicaciones

H. Gallego \* \*\*, E. Toro <sup>1</sup> \*\*, R. Rojas \*\* \*\* \*\*

\* Universidad del Valle – Cali, COLOMBIA

\*\* Universidad Nacional a Distancia – Cali, COLOMBIA

\*\*\* Universidad – ICESI, Cali, COLOMBIA

Fecha de Recepción: 23/01/2020

Fecha de Aceptación: 07/04/2020

PAG 119-125

### Abstract

*A brief presentation is made on the problem of fly ash from sugar production, which can be transformed into pozzolan through physical, thermal, chemical or mixed activation, and then used as a chemical corrector and additive for the production of Portland cement. The conversion of the ash into pozzolans is carried out with hydrothermal processes that include repetitive actions of incubation, filtration and drying, for which an alkali solution is used at high temperatures, where compounds such as zeolites are formed from the amorphous aluminosilicates present, being necessary in some cases to adjust the Si/Al ratio to produce the desired type of pozzolan. It is concluded that the use of fly ash, as a chemical corrector in the raw clinker mix, depends on the purity of the limestone and the evaluation of the chemical balance of the mix.*

*Keywords: Pozzolan; fly ash; industrial byproducts; sustainability*

### Resumen

Se hace una breve presentación sobre el problema de las cenizas volantes provenientes de la producción de azúcar, las cuales se pueden transformar en puzolana por medio de activación física, térmica, química o mixta, para luego ser utilizadas como corrector químico y adición para la producción de cemento Portland. La conversión de las cenizas en puzolanas se lleva a cabo con procesos hidrotérmicos que incluyen acciones repetitivas de incubación, filtración y secado, para lo cual se utiliza una solución alcalina a altas temperaturas, en donde se forman compuestos como zeolitas a partir de los aluminosilicatos amorfos presentes, siendo necesario en algunos casos, ajustar la proporción de Si/Al para producir el tipo de puzolana deseada. Se concluye que el uso de cenizas volantes, como corrector químico en la mezcla cruda del clínker, depende de la pureza de la piedra caliza y de la valoración del balance químico de la mezcla.

**Palabras clave:** Puzolana; ceniza volante; subproductos industriales; sostenibilidad

## 1. Introduction

*In energy cogeneration, different types of organic materials can be used, alone or mixed together, such as municipal solid waste, sewage plant sludge, biomass, bagasse, and coal, and it is necessary to know and adapt the incineration (combustion) technologies to the energy requirements of the fuel (Gallego Ocampo, 2015). In the Colombian sugar industry, it is very common to use the coal-bagasse mixture as a fuel in power boilers, due to the thermodynamic capacity generated (high calorific value) for the production of electrical, mechanical and thermal power (Margallo et al., 2015); (Mohee et al., 2015).*

*During combustion, large quantities of ash are generated, which are considered to be waste. Therefore, in most cases, the sugar industry disposes of the ash on roads and empty lots, thus wasting the potential of the byproduct as a cementing agent, a substitute for clinker and cement in mortars and concrete, since the ash contains in its structure pozzolanic minerals such as Al, Si, K, Ca, Br, Fe, Mg, Na, Mn with their corresponding oxides ( $Al_2O_3$ ,  $SiO_2$ ,  $SiO_4$ ,  $K_2O$ ,  $CaO$ ,  $Br$ ,  $Fe_2O_3$ ,  $MgO$ ,  $Na_2O$ ,  $MnO$ ). These react chemically during combustion resulting in the formation of quartz ( $SiO_2$ ) and corundum ( $Al_2O_3$ ) at 560°C due to the presence of Ca and S and the fusion of quartz, silica and alumino-silicates at temperatures between 600°C and 800°C. However, anorthite ( $CaAl_2Si_2O_8$ ) is formed at 700°C when CaO reacts with  $Al_2O_3$  and  $SiO_2$  (Jagadesh and Ramchandramurthy, 2015); (Melissari, 2012); (Van Dyk, 2006); (Zhang et al., 2013a).*

---

#### Corresponding author:

Universidad Nacional a Distancia – Cali, COLOMBIA  
E-mail: efertoro@hotmail.com



## 2. Ash

Ash is the final product of the combustion reaction at temperatures between 1200°C and 1700°C, where the fuel can be coal, bagasse, sludge, municipal solid waste and the oxidizing agent can be air and/or gas. During combustion, processes of vaporization, precipitation, nucleation and coalescence take place, as shown in (Figure 1). In this case, the organic and inorganic parts of the fuel undergo chemical and physical transformations at high temperatures (Mejía et al., 2014); (Melissari, 2012).


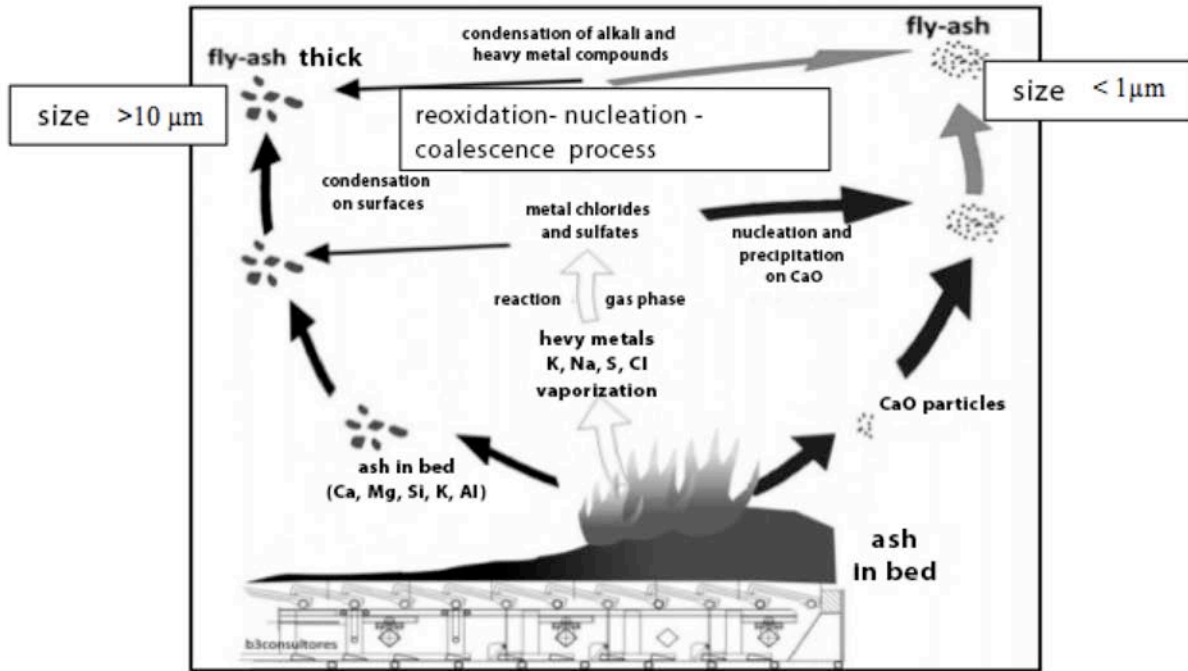


Figure 1. Ash formation mechanism. Source: (Melissari, 2012)

The ash may contain alumina and silica compounds including mullite, quartz, hematite and calcite and some inorganic compounds such as lime and sulfates, where, at low calcium contents, crystalline compounds such as quartz and mullite predominate, while at high calcium contents aluminosilicates such as tricalcium aluminate, calcium silicate and tetracalcium aluminosilicate predominate (Fotovát et al., 2009); (Jankowski et al., 2006). On the other hand, if the sugar cane bagasse is calcined at 600°C for 6 hours, ash can be obtained with a weight percentage of 84% SiO<sub>2</sub> in both crystalline and amorphous phases (Paula et al., 2009).

## 3. Pozzolanic Materials

Pozzolanic materials are characterized by mineral particle packing, where the amorphous silica when in contact with water solubilizes and reacts with the Ca<sup>2+</sup> ions present in Ca(OH)<sub>2</sub>, forming hydrated hydroxide silicates similar to those produced in cement hydration reactions as shown in (Equation 1), where the high silica, alumina and iron oxide content favors the pozzolanic activity of the ash (Abiodun and Jimoh, 2018); (Ribeiro and Morelli, 2014).



The pozzolanicity of a siliceous and aluminous compound is a function of the chemical composition, the amorphousness of the phases, and the fineness. These variables depend on the activation temperature (between 600°C and 800°C), the capture method (wet or dry) and the storage method since if the material is captured wet, the treatment process becomes complicated (Ribeiro and Morelli, 2014).



The ash as it leaves the incineration process would have a low pozzolanic activity due to its large particle size. In this case, the ash would act as an inert material or without activity (filler), so it is necessary to submit it to grinding and sieving processes (Kumar and Kumar, 2011); (Margallo et al., 2015); (Park et al., 2016); (Sahoo, 2016);). The average pozzolan particle size can vary between 6 and 13  $\mu\text{m}$  depending on the gradation, distribution and fineness of the cement (Bentz et al., 2011); (Erdođdu and Türker, 1998); (Givi et al., 2010); (Seraj et al., 2017). Coincidentally, in Colombia, cement is made with a particle size between 8 and 14  $\mu\text{m}$  (Mendoza et al., 2014); (Tobón and Restrepo, 2010).

#### 4. Physicochemical processing for the activation of ash as pozzolan

The physicochemical changes of volume and surface occurring in the ash during size reduction favor the reversible desorption of water, chemical reactivity for ion exchange during mineral transformations, the formation of alkali metal silicates (K, Na) by the fusion and chemical interaction of quartz and silica with other components of the ash. They occur by the fusion of aluminosilicates; the decomposition of carbonates, oxalates, chlorides, and other inorganic salts; the volatilization of alkaline and other heavy metals; the fragmentation of particles by thermal shock and rapid emission of gases from them; the coalescence and agglomeration of mineral particles (Blissett, 2012); (Hela et al., 2013); (Sahoo, 2016).

When the ash is subjected to hydrothermal processes in an alkali solution such as NaOH,  $\text{Na}_2\text{CO}_3$ ,  $\text{NaNO}_3$ ,  $\text{CaCl}_2 \cdot 2\text{H}_2\text{O}$ ,  $\text{Ca}(\text{NO}_3)_2$  and KOH at high temperatures, it tends to form new compounds such as zeolites from the amorphous aluminosilicates present, which dissolve in the reaction mixture and then group, nucleate and grow as crystals on the surface of the coal ash (because of the presence of trace elements such as  $\text{TiO}_2$ , MnO, MgO,  $\text{Na}_2\text{O}$  and  $\text{K}_2\text{O}$ , carbonates and sulfates). The degree of dissolution of aluminosilicates determines the conversion percentage and the speed of the pozzolanic formation, which can be affected by chemical factors, such as the amount of calcium hydroxide available for the reaction, nature of the active phase,  $\text{SiO}_2$  content in the ash,  $\text{Ca}(\text{OH})_2$ /aluminosilicate ratio, crystallographic composition, alkalinity of the aqueous phase, Si/Al ratio, reaction time and physical factors such as surface area, solid/water ratio, temperature, pressure, heating sources (conventional ovens, autoclaves, microwaves (MW), ultrasound (US), among other sources). In some cases, it is necessary to adjust the Si/Al ratio by adding aluminates or silicates to produce the desired type of pozzolan. The evaluation of the effectiveness of the chemical treatment is determined by activation tests or pozzolanicity indicator tests such as the Frattini test or the mechanical activity index performed for Portland cement (Hollman et al., 1999); (Muraza et al., 2013); (Ribeiro and Morelli, 2014); (Zhang et al., 2013a).

Direct hydrothermal synthesis of pozzolan (incubation-induction period) is performed by mixing 500 g of fly ash in 1.25  $\text{dm}^3$  of a 2 M NaOH solution, followed by heat treatment at 90°C for 96 h. During this time, the Si concentration is stabilized at 6800  $\text{mg}/\text{dm}^3$ . During the process, a maximum concentration of Si is reached (start of crystallization), while the aluminum reaches a maximum concentration at the beginning of the reaction and then it decreases to zero, one hour after the start of the Si crystallization process. At 400°C and 600°C, the carbon is lost during calcination and at 800°C crystalline silica compounds are formed, causing a decrease in the pozzolanic activity. Therefore, the optimum temperature to generate amorphous silica with a pozzolanic activity index of 77% and an ignition loss of 5.7% is 600°C (Cordeiro et al., 2009); (Feng et al., 2018).

Other hydrothermal treatments include repetitive actions of incubation, filtration and drying (solid residue - crystal formation) at the same mixing and incubation conditions but at different times to adjust the Si/Al molar ratio between 0.8 and 2. The first incubation process is carried out for 6 h, and then it is submitted to the filtration process to separate the solid residue (formed crystals) and adjust the filtration. The solid residue is dried, while the Si/Al molar ratio is adjusted to the filtration. In the second process, the adjusted filtration is incubated for 48 h, while the filtration and drying are carried out again. The new filtration is mixed with the solid residue obtained during the first incubation process and incubated again for 24 h (Behin et al., 2016).

Conventional hydrothermal methods for ash conversion are industrially inefficient due to excessive time and associated costs and low efficiency in the production of zeolites, as well as the amount of water used to neutralize the NaOH solution since, after the activation treatment, it becomes a problem when disposing the liquid into the sewage system. However, the same treatments have been carried out but with zero emissions to the sewage system, reducing water and NaOH consumption between 50% and 90%, by recirculating the NaOH solution along the process (Behin et al., 2016).

The pozzolan formation process (hydrothermal synthesis) with microwaves allows to shorten the crystallization time by the homogeneous heating of the synthesis mixture at atmospheric pressure and to accelerate the nucleation process (fast reaction speed), thus producing pure zeolite crystals with different morphologies, thanks to inductive heating, the specific dissipation of energy in the water molecules present in the surface boundary layer and the immobilization of heavy metal ions and cations such as Ba, Cu, Cr, Mn, Ni, Pb and V



present in the ash, while the same amount of Si and Al is dissolved (Bukhari et al., 2014); (Kim and Lee, 2009); (Muraza et al., 2013); (Tanaka et al., 2008); (Zhang et al., 2013b).

Also, the ultrasonic treatment carried out at 300 W with alkaline solutions with NaOH concentrations between 1 M and 5 M (at a solid-liquid ratio of 0.5 g/cm<sup>3</sup>) at different time intervals between 30 minutes and 2 h improves mass transfer from acoustic cavitation and the collapse of microbubbles generated in the liquid phase, producing a phase change corresponding to the formation of hydroxysodalite. This accelerates chemical processes such as the dissolution of Al/Si, strengthens the bonds of particles at the solid/gel interface (increased crystallization), and accelerates the speed of the secondary nucleation (Andaç et al., 2005); (Belviso et al., 2011); (Hums et al., 2015); (Wang and Zhu, 2005).

## 5. Uses of Pozzolan

The use of pozzolans in cement factories as a chemical corrector and additive for the production of Portland cement provides significant advantages at both an economic and environmental level because by replacing a portion of the Portland cement with pozzolans, the generation of greenhouse gases produced during the calcination of the limestone (CaO) when producing cement is reduced while operating costs are also reduced (Gorai and Ash, 2018).

### 5.1 Chemical corrector for the obtaining of Clinker

A chemical corrector is a raw material that exposes a high composition of silica oxide (SiO<sub>2</sub>), iron (Fe<sub>2</sub>O<sub>3</sub>), and aluminum (Al<sub>2</sub>O<sub>3</sub>). It is added to a mixture of crushed limestone and clay slurry to obtain the clinker, where the chemical composition is a conclusive element in the development of the cementitious properties so that the quality of the clinker depends on the chemical control of the slurry (Enríquez, 2019).

The chemical correctors are added to balance the composition of the clinker components (calcium silicates, tricalcium aluminate, and calcium aluminoferrite), which are generated in the sintering of the clays and limestone. The balance is made when the quantity of the compounds present in the raw mixture is not enough to produce the clinker. Materials called "second raw materials" are used such as clay, shale, sand, iron ore, bauxite, fly ash, and slag (Benzaazoua et al., 2010).

The proportion of fly ash used as a chemical corrector in the raw clinker mixture ranges from 5% to 25%, although it depends on the purity of the limestone and the assessment of chemical balance (Ferrari et al., 2012). The advantages of using industrial byproducts as a chemical corrector are reduced operating costs associated with the primary raw material and improved physicochemical properties of Portland cement (Enríquez, 2019). On the other hand, the requirements for a chemical corrector are low levels of impurities to avoid problems in the manufacture of the clinker, as in the case of magnesium oxide (MgO), which compromises the durability of the cement if its raw material content is greater than 5% (Ahmaruzzaman, 2010); (Blissett, 2012); (Mayor, 2014); (Toro et al., 2014).

### 5.2 Portland Cement Additive

The industrial byproduct is considered pozzolan if the concentration of calcium hydroxide in solution is less than the saturation concentration. The pozzolanic effect is established by a decrease in the concentration of CaO in the liquid phase since the calcium hydroxide generated through the hydration of the cement is sequestered and combined by the pozzolan (Ribeiro and Morelli, 2014).

Due to their physicochemical characteristics, fly ash is used as an additive for prefabricated and cement clinker because of its high pozzolanic potential (Rougeau, 2004). The addition of bagasse fly ash with pozzolanic reactivity can form composites with cementitious properties that meet the standards given in Colombian NTC 3493 and US ASTM C618 standards (ASTM, 2005); (Icontec, 2017). Although care must be taken when using bagasse ash as an additive, since an excess of organic material produces unburned products that contain alkaline sulfates, which react with tricalcium aluminate, forming ettringite. This is an expansive substance that affects the mechanical properties and durability of the composite (Valencia et al., 2018). Therefore, there are limitations in the use of pozzolans from bagasse ash, in the case of the percentage of coal. This mineral is the remainder of the result of the mixture of mineral coal and bagasse, which is known in the industry as "unburned products". For this reason, it is recommended that the mineral be less than 5% since it forms components that negatively influence the durability and properties of hydraulic concrete (Camilo and Gutiérrez, 2006); (Ribeiro and Morelli, 2014).

The substitution of CaO and OH<sup>-</sup> ions by ash from bagasse generates a pozzolanic reactivity independent of the temperature of ash calcination (Onésippe et al., 2010); (Ribeiro and Morelli, 2014). In a concrete mix, it is feasible to replace between 10% and 50% of the ordinary Portland cement with pozzolanic bagasse ash, which can increase the durability of the concrete, especially the resistance to chloride penetration (Nunes, 2009); (Paula





et al., 2009); (Rerkpiboon et al., 2015); (Xu et al., 2018). However, the substitution of bagasse ash in the 15% - 20% range by Portland cement produces the best performance in compressive strength tests (Pereira et al., 2018).

## 6. Conclusions

The high content of silica, alumina and iron oxide favors the pozzolan activity of the ash, so its reactivity depends on the chemical composition, phase amorphousness and fineness, as well as the activation temperature. It is necessary to establish the hydrothermal synthesis method that best suits the chemical requirements for the activation of the ash as pozzolans.

To obtain ash with a SiO<sub>2</sub> content of 84% (weight percentage), both in the crystalline and the amorphous phases, a thermal activation process must be carried out at calcination temperatures around 600°C for 6 hours (hydrothermal synthesis). The degree of dissolution of the aluminosilicates in the ash determines the conversion rate and the speed of the formation of pozzolan.

Conventional hydrothermal methods for the transformation of ash into pozzolans are industrially ineffective. On the contrary, modern pozzolan-forming processes, such as hydrothermal synthesis with microwaves and ultrasound, allow the efficient transformation of the byproduct into pozzolans.

The use of fly ash from sugar cane bagasse as a chemical corrector in the raw clinker mix will depend on the purity of limestone and the assessment of the chemical balance, so up to 20% of the Portland cement can be replaced in a concrete mix and the compressive strength can be improved.

## 7. References

- Abiodun, Y. O.; Jimoh, A. A. (2018).** Microstructural characterisation, physical and chemical properties of rice husk ash as viable Pozzolan in building material: a case study of some Nigerian grown rice varieties. *Nigerian Journal of Technology*, 37(1), 71. <https://doi.org/10.4314/njt.v37i1.10>.
- Ahmaruzzaman, M. (2010).** A review on the utilization of fly ash. *Progress in Energy and Combustion Science*. 36(3), 327-363. <https://doi.org/10.1016/j.peccs.2009.11.003>.
- Andaç, Ö.; Tatlier, M.; Sirkecioğlu, A.; Ece, I.; Erdem-Şenatalar, A. (2005).** Effects of ultrasound on zeolite A synthesis. *Microporous and Mesoporous Materials*, 79(1), 225–233. <https://doi.org/https://doi.org/10.1016/j.micromeso.2004.11.007>.
- ASTM C. (2005).** C-618-19: Standard Specification for Coal Fly Ash and Raw or Calcined Natural Pozzolan for Use in Concrete (ASTM). Annual Book of ASTM Standard.
- Behin, J.; Bukhari, S. S.; Kazemian, H.; Rohani, S. (2016).** Developing a zero liquid discharge process for zeolitization of coal fly ash to synthetic NaP zeolite. *Fuel*, 171, 195–202. <https://doi.org/https://doi.org/10.1016/j.fuel.2015.12.073>.
- Belviso, C.; Cavalcante, F.; Lettino, A.; Fiore, S. (2011).** Effects of ultrasonic treatment on zeolite synthesized from coal fly ash. *Ultrasonics Sonochemistry*, 18(2), 661–668. <https://doi.org/https://doi.org/10.1016/j.ultsonch.2010.08.011>.
- Bentz, D. P.; Ferraris, C. F.; Filliben, J. J. (2011).** Optimization of Particle Sizes in High Volume Fly Ash Blended Cements. NISTIR 7763.
- Benzaazoua, M.; Peyronnard, O.; Belem, T.; Stephant, A.; Dublet, G. (2010).** Key issues related to behaviour of binders in cemented paste backfilling. *Proceedings of the Thirteenth International Seminar on Paste and Thickened Tailings*, (December 2015), 345–363. [https://doi.org/10.36487/acg\\_rep/1063\\_30\\_benzaazoua](https://doi.org/10.36487/acg_rep/1063_30_benzaazoua).
- Blissett, R. S.; Rowson, N. A. (2012).** A review of the multi-component utilisation of coal fly ash. *Fuel*, 97, 1–23. <https://doi.org/10.1016/j.fuel.2012.03.024>.
- Bukhari, S. S.; Behin, J.; Kazemian, H.; Rohani, S. (2014).** A comparative study using direct hydrothermal and indirect fusion methods to produce zeolites from coal fly ash utilizing single-mode microwave energy. *Journal of Materials Science*, 49(24), 8261–8271. <https://doi.org/10.1007/s10853-014-8535-2>.
- Camilo, J.; Gutiérrez, R. (2006).** Efectos de la adición de metacaolín en el cemento pórtland. *Dyna*, 73(150), 131–141.
- Cordeiro, G. C.; Toledo Filho, R. D.; Fairbairn, E. M. R. (2009).** Effect of calcination temperature on the pozzolanic activity of sugar cane bagasse ash. *Construction and Building Materials*, 23(10), 3301–3303. <https://doi.org/10.1016/j.conbuildmat.2009.02.013>.
- Enríquez, M. (2019).** Aprovechamiento de residuos industriales para la obtención de clínker. Tesis de investigación presentada como requisito parcial para optar al título de:
- Magister en Ingeniería Ambiental. Universidad Nacional de Colombia, Facultad de Ingeniería, Departamento de Ingeniería Química. Bogotá, Colombia. <http://bdigital.unal.edu.co/73314/2/MaryeniEnr%C3%ADquez.2019.pdf>.
- Erdođdu, K.; Türker, P. (1998).** Effects of fly ash particle size on strength of portland cement fly ash mortars. *Cement and Concrete Research*, 28(9), 1217–1222. [https://doi.org/10.1016/S0008-8846\(98\)00116-1](https://doi.org/10.1016/S0008-8846(98)00116-1).
- Feng, W.; Wan, Z.; Daniels, J.; Li, Z.; Xiao, G.; et al. (2018).** Synthesis of high quality zeolites from coal fly ash: Mobility of hazardous elements and environmental applications. *Journal of Cleaner Production*, 202, 390–400. <https://doi.org/10.1016/j.jclepro.2018.08.140>.
- Ferrari, L.; Kaufmann, J.; Winnefeld, F.; Plank, J. (2012).** Reaction of clinker surfaces investigated with atomic force microscopy. *Construction and Building Materials*, 35, 92–96. <https://doi.org/10.1016/j.conbuildmat.2012.02.089>.
- Fotovat, F.; Kazemini, M.; Kazemian, H. (2009).** Novel utilization of zeolited fly ash hosting cobalt nanoparticles as a catalyst applied to the Fischer-Tropsch synthesis. *Catalysis Letters*, 127(1–2), 204–212. <https://doi.org/10.1007/s10562-008-9671-6>.
- Gallego Ocampo, H. L. (2015).** Reactivity of the co-combustion of coal-sludge. *UG Ciencia* 21, 91-102.
- Givi, A. N.; Rashid, S. A.; Aziz, F. N. A.; Salleh, M. A. M. (2010).** Assessment of the effects of rice husk ash particle size on strength, water permeability and workability of binary blended concrete. *Construction and Building Materials*, 24(11), 2145–2150. <https://doi.org/10.1016/j.conbuildmat.2010.04.045>.
- Gorai, S.; Ash, F. (2018).** Utilization of Fly ash for sustainable environment management.



- Hela, R.; Orsakova, D.; Orsáková, D. (2013).** The mechanical activation of fly ash. *Procedia Engineering*, 65(November), 87–93. <https://doi.org/10.1016/j.proeng.2013.09.016>.
- Hollman, G. G.; Steenbruggen, G.; Janssen-Jurkovičová, M. (1999).** A two-step process for the synthesis of zeolites from coal fly ash. *Fuel*, 78(10), 1225–1230. [https://doi.org/https://doi.org/10.1016/S0016-2361\(99\)00030-7](https://doi.org/https://doi.org/10.1016/S0016-2361(99)00030-7).
- Hums, E.; Musyoka, N. M.; Baser, H.; Inayat, A.; Schwieger, W. (2015).** In-situ ultrasound study of the kinetics of formation of zeolites Na-A and Na-X from coal fly ash. *Research on Chemical Intermediates*, 41(7), 4311–4326. <https://doi.org/10.1007/s11164-014-1531-y>.
- Icontec (2017).** NTC 3493: Civil Engineering And Architecture. Fly Ash And Raw Or Calcined Natural Pozzolan For Use In Concrete. Icontec.
- Jagadesh, P.; Ramachandramurthy, A. (2015).** Micro-analytical studies on sugar cane bagasse ash. *Sadhana*, volumen 40 (August), 1629–1638.
- Jankowski, J.; Ward, C. R.; French, D.; Groves, S. (2006).** Mobility of trace elements from selected Australian fly ashes and its potential impact on aquatic ecosystems. *Fuel*, 85(2), 243–256. <https://doi.org/10.1016/j.fuel.2005.05.028>.
- Kim, J. K.; & Lee, H. D. (2009).** Effects of step change of heating source on synthesis of zeolite 4A from coal fly ash. *Journal of Industrial and Engineering Chemistry*, 15(5), 736–742. <https://doi.org/https://doi.org/10.1016/j.jiec.2009.09.055>.
- Kumar, S.; Kumar, R. (2011).** Mechanical activation of fly ash: Effect on reaction, structure and properties of resulting geopolymer. *Ceramics International*, 37(2), 533–541. <https://doi.org/10.1016/j.ceramint.2010.09.038>.
- Margallo, M.; Taddei, M. B. M.; Hernández-Pellón, A.; Aldaco, R.; Irabien, Á. (2015).** Environmental sustainability assessment of the management of municipal solid waste incineration residues: A review of the current situation. *Clean Technologies and Environmental Policy*, 17(5), 1333–1353. <https://doi.org/10.1007/s10098-015-0961-6>.
- Mayor, J. D. L. (2014).** Efecto de las cenizas volantes tratadas térmicamente como sustituto parcial del cemento en morteros. Proyecto de grado presentado como requisito para optar por el título de Ingeniero de Materiales. Universidad de San Buenaventura, Facultad de Ingeniería, Programa Ingeniería de Materiales. Santiago de Cali, Colombia.
- Mejía, J. M.; Rodríguez, E. D.; De Gutiérrez, R. M. (2014).** Utilización potencial de una ceniza volante de baja calidad como fuente de aluminosilicatos en la producción de geopolímeros. *Ingeniería y Universidad*, 18(2), 309–327. <https://doi.org/10.11144/Javeriana.IYU18-2.upcv>.
- Melissari, B. (2012).** Comportamiento de Cenizas y su Impacto en Sistemas de Combustión de Biomasa. *Memoria de Trabajos de Difusión Científica y Técnica*, 10, 69–82.
- Mendoza, O.; Sierra, G.; Tobón, J. I. (2014).** Effect of the reagglomeration process of multi-walled carbon nanotubes dispersions on the early activity of nanosilica in cement composites. *Construction and Building Materials*, 54, 550–557. <https://doi.org/10.1016/j.conbuildmat.2013.12.084>.
- Mohee, R.; Boojhawon, A.; Sewhoo, B.; Rungasamy, S.; Somaroo, G. D.; Mudhoo, A. (2015).** Assessing the potential of coal ash and bagasse ash as inorganic amendments during composting of municipal solid wastes. *Journal of Environmental Management*, 159, 209–217. <https://doi.org/10.1016/j.jenvman.2015.05.008>.
- Muraza, O.; Bakare, I. A.; Tago, T.; Konno, H.; Adedigba, A. lateef, Al-Amer, A. M.; et al. (2013).** Controlled and rapid growth of MTT zeolite crystals with low-aspect-ratio in a microwave reactor. *Chemical Engineering Journal*, 226, 367–376. <https://doi.org/10.1016/j.cej.2013.04.072>.
- Nunes, I. H. S. (2009).** Estudo Das Características Físicas E Químicas Da Cinza Do Bagaço De Cana-De-Açúcar Para Uso Na Construção. *Revista Tecnológica*, V.17 (1) <http://www.periodicos.uem.br/ojs/index.php/RevTecnol/article/view/8728>.
- Onésippe, C.; Passe-Coutrin, N.; Toro, F.; Delvasto, S.; Bilba, K.; Arsène, M. A. (2010).** Sugar cane bagasse fibres reinforced cement composites: Thermal considerations. *Composites Part A: Applied Science and Manufacturing*, Volume 41 (4), 549–556 <https://www.sciencedirect.com/science/article/pii/S1359835X10000096>.
- Park, S. M.; Jang, J. G.; Lee, N. K.; Lee, H. K. (2016).** Physicochemical properties of binder gel in alkali-activated fly ash/slag exposed to high temperatures. *Cement and Concrete Research*, 89, 72–79. <https://doi.org/10.1016/j.cemconres.2016.08.004>.
- Patil, A. G.; Anandhan, S. (2012).** Ball Milling of Class-F Indian Fly Ash Obtained from a Thermal Power Station. *International Journal of Energy Engineering(IJEE)*, 2 (2), 57–62.
- Paula, M. O. De; Tinóco, I. D. F. F.; Rodrigues, C. D. S.; Saraz, J. A. O. (2009).** Sugarcane Bagasse Ash as a Partial-Portland-Cement- Replacement material. *Dyna*, 77(163), 47–54.
- Pereira, A. M.; Moraes, J. C. B.; Moraes, M. J. B.; Akasaki, J. L.; Tashima, M. M.; Soriano, L.; Monzó, J.; Payá, J. (2018).** Valorisation of sugarcane bagasse ash (SCBA) with high quartz content as pozzolanic material in Portland cement mixtures. *Materiales de Construcción*, 68 (330), 1–10. <https://doi.org/10.3989/mc.2018.00617>.
- Rerkpiboon, A.; Tangchirapat, W.; Jaturapitakkul, C. (2015).** Strength, chloride resistance, and expansion of concretes containing ground bagasse ash. *Construction and Building Materials*, 101, 983–989. <https://doi.org/10.1016/j.conbuildmat.2015.10.140>
- Ribeiro, D. V.; Morelli, M. R. (2014).** Effect of Calcination Temperature on the Pozzolanic Activity of Brazilian Sugar Cane Bagasse Ash (SCBA). *Materials Research*. vol.17 no.4 <https://doi.org/10.1590/S1516-14392014005000093>.
- Rougeau, P. (2004).** Ultra-high-performance concretes: First recommendations and examples of application. In *Proceedings of the fib Symposium 2004 - Concrete Structures: The Challenge of Creativity*.
- Sahoo, S. (2016).** A Review of Activation Methods in Fly Ash and the Comparison in Context of Concrete Strength. *Journal of Basic and Applied Engineering Research*, 3(10), 883–887.
- Seraj, S.; Cano, R.; Ferron, R. D.; Juenger, M. C. G. (2017).** The role of particle size on the performance of pumice as a supplementary cementitious material. *Cement and Concrete Composites*, 80, 135–142. <https://doi.org/10.1016/j.cemconcomp.2017.03.009>.
- Sevim, O.; Demir, I. (2016).** Particle size optimization of fly ash. *International Journal of Advances in Mechanical and Civil Engineering (IJAMCE) Volume-4, Issue-1*. pp. 85-87.
- Tanaka, H.; Fujii, A.; Fujimoto, S.; Tanaka, Y. (2008).** Microwave-assisted two-step process for the synthesis of a single-phase Na-A zeolite from coal fly ash. *Advanced Powder Technology*, 19(1), 83–94. <https://doi.org/10.1163/156855208X291783>.
- Tobón, D.; Restrepo, O. J. (2010).** Comparative Analysis of Performance of Portland Cement Blended With Nanosilica and Silica Fume. *DYNA*, Volumen 77, Número 163, p. 37-46.
- Toro, F.; Gordillo, M.; Delvasto, S.; Savastano, H. (2014).** Modelación del módulo de la resistencia a la flexión de un material compuesto cementicio a partir de propiedades en estado fresco. *Revista Ingeniería de Construcción*, 29(1), 115–127. <https://doi.org/10.4067/S0718-50732014000100008>.
- Valencia Saavedra, W. G.; Angulo Ramírez, D. E.; Mejía de Gutiérrez, R. (2018).** Resistencia química de concretos de activación alcalina ceniza volante/ escoria: Sulfatos y ácidos. *Informador Técnico*, 82(1), 67-77. <https://doi.org/10.23850/22565035.1351>.
- Van Dyk, J. C. (2006).** Understanding the influence of acidic components (Si, Al, and Ti) on ash flow temperature of South African coal sources. *Minerals Engineering*, 19 (3), 280–286. <https://doi.org/10.1016/j.mineng.2005.06.018>

ENGLISH VERSION.....

- Wang, S.; Zhu, Z. H. (2005).** Sonochemical treatment of fly ash for dye removal from wastewater. *Journal of Hazardous Materials*, 126(1), 91–95. <https://doi.org/https://doi.org/10.1016/j.jhazmat.2005.06.009>.
- Xu, Q.; Ji, T.; Gao, S. J.; Yang, Z.; Wu, N. (2018).** Characteristics and applications of sugar cane bagasse ash waste in cementitious materials. *Materials*, 12 (1). <https://doi.org/10.3390/ma12010039>.
- Zhang, X.; Tang, D.; Jiang, G. (2013a).** Synthesis of zeolite NaA at room temperature: The effect of synthesis parameters on crystal size and its size distribution. *Advanced Powder Technology*, 24(3), 689–696. <https://doi.org/10.1016/J.APT.2012.12.010>.

